

# HALLIBURTON

## Cementing Gulf of Mexico, Broussard

### LAB RESULTS - Lead

#### Job Information

Request/Slurry	65112/3	Rig Name	TRANSOCEAN HORIZON	Date	February 10th 2010
Submitted By	Jesse Gaigliano	Job Type	Production Casing	Bulk Plant	Fourchon-C-Port I, La, USA
Customer	BP	Location	Mississippi Cny	Well	Mississippi Canyon 252 OCS-G-32306 Macardo #1

#### Well Information

Casing/Liner Size	9 5/8"	Depth MD	19650 ft	BHST	262 F
Hole Size	12 1/4"	Depth TVD	19650 ft	BHCT	223 F

#### Drilling Fluid Information

Mud Company	MI	Type	SOBM	Density	14.6 PPG	PV/YP
-------------	----	------	------	---------	----------	-------

#### Cement Information - Lead Design

Conc	UOM	Cement/Additive	Sample Type	Sample Date	Lot No.	Cement Properties	
						Slurry Density	16.741 PPG
						Slurry Yield	1.37 FT3
100.00	% BWO	Lafarge Class H	Bulk	Dec 29, 2009	LOCATI ON	Water Requirement	4.84 GPS
0.07	% BWO	EZ-FLO	Bulk	Dec 29, 2009	BLEND ED	Total Mix Fluid	5.04 GPS
0.25	% BWO	D-Air 3000	Bulk	Dec 29, 2009	BLEND ED	Foam Density	14.496 PPG
						Foam Quality	12.88 %
1.88	lb/sk	KCl (Potassium Chloride) Salt	Bulk	Dec 29, 2009	BLEND ED	Water Source	Fresh Water
20.00	% BWO	SSA-1 (Silica Flour) - PB	Bulk	Dec 29, 2009	BLEND ED	Water Chloride	N/A ppm
15.00	% BWO	SSA-2 (100 Mesh) - PB	Bulk	Dec 29, 2009	BLEND ED		
0.20	% BWO	SA-541	Bulk	Dec 29, 2009	BLEND ED		
0.11	gps	ZoneSealant 2000	Lab	Mar 15, 2009			
0.20	gps	SCR-100L	Lab	Dec 23, 2008	2117		
4.84	gps	Fresh Water	Lab	Jan 18, 2010			

#### Operation Test Results Request ID 65112/3

##### Thickening Time, Request Test ID: 722097

Temp (°F)	Pressure (psi)	Batch Mix (min)	Reached in (min)	Start BC	30 Bc (hh:mm)	40 Bc (hh:mm)	50 Bc (hh:mm)	70 Bc (hh:mm)
223	15,945	0	89	7	04:57	04:58	04:59	05:00

##### Mud Balance Density, Request Test ID: 722106

Density (ppg)  
16.5

##### Mixability (0 - 5) - 0 is not mixable, Request Test ID: 722100

Mixability rating (0 - 5)  
5

##### Foam Mix and Stability, Request Test ID: 727534

This report is the property of Halliburton Energy Services and neither it nor any part thereof, nor a copy thereof, is to be published or disclosed without first securing the expressed written approval of Halliburton. It may however be used in the course of regular business operations by any person or concern receiving such report from Halliburton. This report is for information purposes only and the content is limited to the sample described. Halliburton makes no warranties, expressed or implied, as to the accuracy of the contents or results. Any user of this report agrees Halliburton shall not be liable for any loss or damage regardless of cause, including any act or omission of Halliburton, resulting from the use hereof.

SG top 1.91 SG bot. 1.91 Conditioning time (hrs:min) 00:00

**FYSA Viscosity Profile & Gel Strength, Request Test ID: 722102**

Test Temp (°F) 80  
foamed fyaa rpms 22 8 5 3 2 2 2 1 3d= 0 6d = 0

**Non API Rheology, Request Test ID: 722103**

Test temp (°F)	600	300	200	100	60	30	20	10	5	3
80	120	58	36	16	8	4	2	2	2	2

**Non API Rheology, Request Test ID: 722104**

Test temp (°F)	600	300	200	100	60	30	20	10	5	3
130	56	28	18	8	4	2	2	2	2	2

**Non API Rheology, Request Test ID: 722105**

Test temp (°F)	600	300	200	100	60	30	20	10	5	3
190	192	108	66	34	20	10	6	2	2	2

**UCA Comp. Strength, Request Test ID: 722098**

End Temp (°F)	Pressure (psi)	50 psi (hh:mm)	500 psi (hh:mm)	12 hr CS (psi)	24 hr CS (psi)	48 hr CS (psi)
262	15,945	02:28	02:42	1,829	1,872	1,946

**Crush Compressive Strength, Request Test ID: 727536**

Time 1 (hrs)	Strength 1	Time 2 (hrs)	Strength 2	Time 3 (hrs)	Strength 3	Time 4 (hrs)	Strength 4	Foam quality
12	0	24	0	36	0	48	0	0


60 hr c/s = 0 72 hr c/s = 0 84 hr c/s = 0 96 hr c/s = 1145

This report is the property of Halliburton Energy Services and neither it nor any part thereof, nor a copy thereof, is to be published or disclosed without first securing the expressed written approval of Halliburton. It may however be used in the course of regular business operations by any person or concern receiving such report from Halliburton. This report is for information purposes only and the content is limited to the sample described. Halliburton makes no warranties, expressed or implied, as to the accuracy of the contents or results. Any user of this report agrees Halliburton shall not be liable for any loss or damage regardless of cause, including any act or omission of Halliburton, resulting from the use hereof.

Temperature: 227 °F  
Cell Temperature: 20 °C

Pressure: 15932 psi

Consistency: 2 Bc

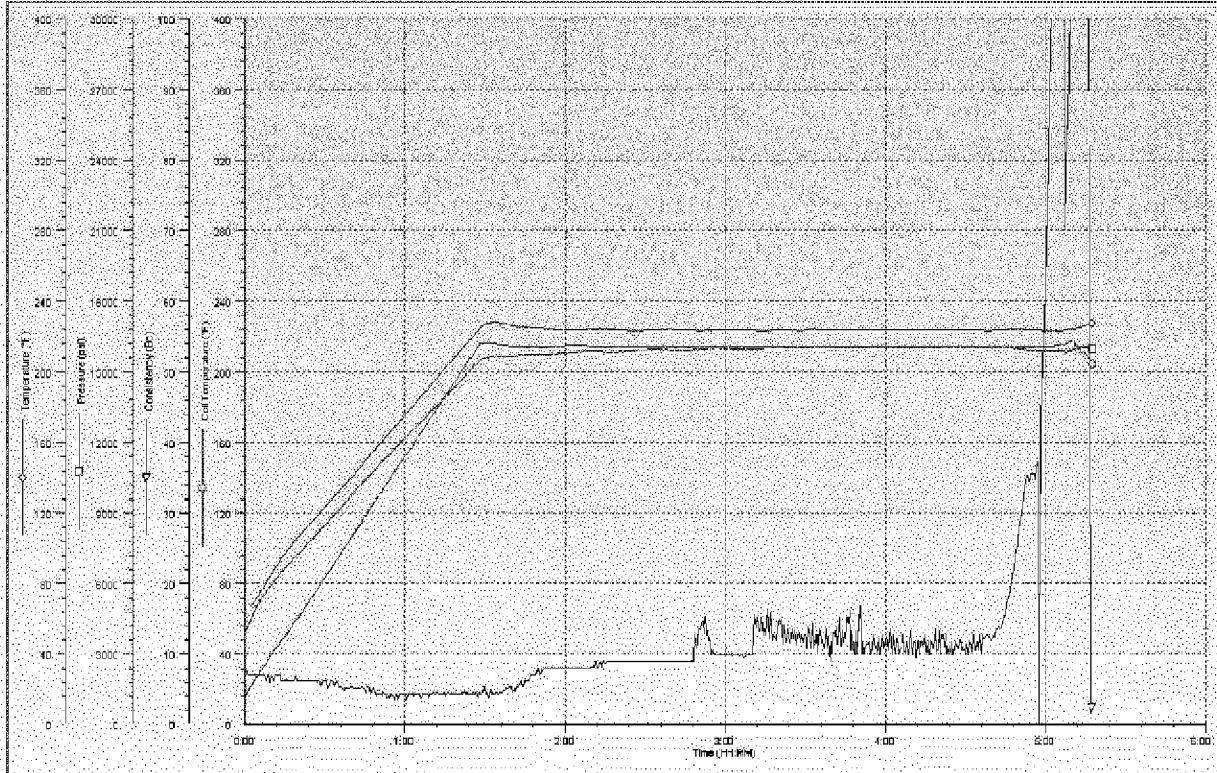


This report is the property of Halliburton Energy Services and neither it nor any part thereof, nor a copy thereof, is to be published or disclosed without first securing the expressed written approval of Halliburton. It may however be used in the course of regular business operations by any person or concern receiving such report from Halliburton. This report is for information purposes only and the content is limited to the sample described. Halliburton makes no warranties, expressed or implied, as to the accuracy of the contents or results. Any user of this report agrees Halliburton shall not be liable for any loss or damage regardless of cause, including any act or omission of Halliburton, resulting from the use hereof.

Well ID:  
Temperature: 281 °F  
Transit Time: 8.89 microsecond

Customer:  
Strength: 1946 psi  
Compressive strength type B (more than 1.4 ft/lb gal)

50 psi @ 2.28:30  
500 psi @ 2.42:00

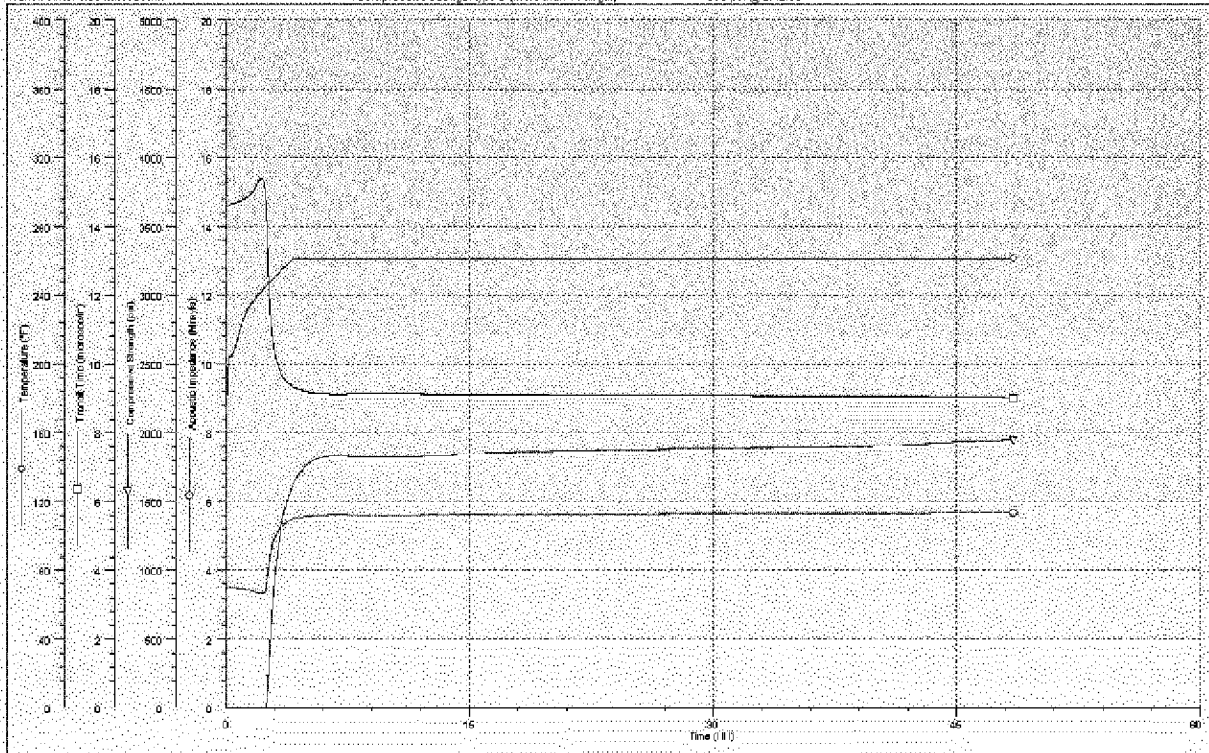

This report is the property of Halliburton Energy Services and neither it nor any part thereof, nor a copy thereof, is to be published or disclosed without first securing the expressed written approval of Halliburton. It may however be used in the course of regular business operations by any person or concern receiving such report from Halliburton. This report is for information purposes only and the content is limited to the sample described. Halliburton makes no warranties, expressed or implied, as to the accuracy of the contents or results. Any user of this report agrees Halliburton shall not be liable for any loss or damage regardless of cause, including any act or omission of Halliburton, resulting from the use hereof.